

RESEARCH OUTPUTS / RÉSULTATS DE RECHERCHE

Three-Dimensional Assemblies of Edge-Enriched WSe₂ Nanoflowers for Selectively Detecting Ammonia or Nitrogen Dioxide

Alagh, Aanchal; Annanouch, Fatima Ezahra; Sierra-Castillo, Ayrton; Haye, Emile; Colomer, Jean François; Llobet, Eduard

Published in:
ACS Applied Materials & Interfaces

DOI:
[10.1021/acsami.2c16299](https://doi.org/10.1021/acsami.2c16299)

Publication date:
2022

Document Version
Publisher's PDF, also known as Version of record

[Link to publication](#)

Citation for published version (HARVARD):
Alagh, A, Annanouch, FE, Sierra-Castillo, A, Haye, E, Colomer, JF & Llobet, E 2022, 'Three-Dimensional Assemblies of Edge-Enriched WSe₂ Nanoflowers for Selectively Detecting Ammonia or Nitrogen Dioxide', *ACS Applied Materials & Interfaces*, vol. 14, no. 49, pp. 54946-54960. <https://doi.org/10.1021/acsami.2c16299>

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal ?

Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Three-Dimensional Assemblies of Edge-Enriched WSe₂ Nanoflowers for Selectively Detecting Ammonia or Nitrogen Dioxide

Aanchal Alagh, Fatima Ezahra Annanouch,* Ayrton Sierra-Castillo, Emile Haye, Jean-François Colomer,* and Eduard Llobet*



Cite This: *ACS Appl. Mater. Interfaces* 2022, 14, 54946–54960



Read Online

ACCESS |



Metrics & More




Article Recommendations



Supporting Information

ABSTRACT: Herein, we present, for the first time, a chemoresistive-type gas sensor composed of two-dimensional WSe₂, fabricated by a simple selenization of tungsten trioxide (WO₃) nanowires at atmospheric pressure. The morphological, structural, and chemical composition investigation shows the growth of vertically oriented three-dimensional (3D) assemblies of edge-enriched WSe₂ nanoplatelets arrayed in a nanoflower shape. The gas sensing properties of flowered nanoplatelets (2H-WSe₂) are investigated thoroughly toward specific gases (NH₃ and NO₂) at different operating temperatures. The integration of 3D WSe₂ with unique structural arrangements resulted in exceptional gas sensing characteristics with dual selectivity toward NH₃ and NO₂ gases. Selectivity can be tuned by selecting its operating temperature (150 °C for NH₃ and 100 °C for NO₂). For instance, the sensor has shown stable and reproducible responses (24.5%) toward 40 ppm NH₃ vapor detection with an experimental LoD < 2 ppm at moderate temperatures. The gas detecting capabilities for CO, H₂, C₆H₆, and NO₂ were also investigated to better comprehend the selectivity of the nanoflower sensor. Sensors showed repeatable responses with high sensitivity to NO₂ molecules at a substantially lower operating temperature (100 °C) (even at room temperature) and LoD < 0.1 ppm. However, the gas sensing properties reveal high selectivity toward NH₃ gas at moderate operating temperatures. Moreover, the sensor demonstrated high resilience against ambient humidity (Rh = 50%), demonstrating its remarkable stability toward NH₃ gas detection. Considering the detection of NO₂ in a humid ambient atmosphere, there was a modest increase in the sensor response (5.5%). Furthermore, four-month long-term stability assessments were also taken toward NH₃ gas detection, and sensors showed excellent response stability. Therefore, this study highlights the practical application of the 2H variant of WSe₂ nanoflower gas sensors for NH₃ vapor detection.

KEYWORDS: gas sensor, transition metal dichalcogenide, tungsten diselenide, chemical vapor deposition, nitrogen dioxide, ammonia

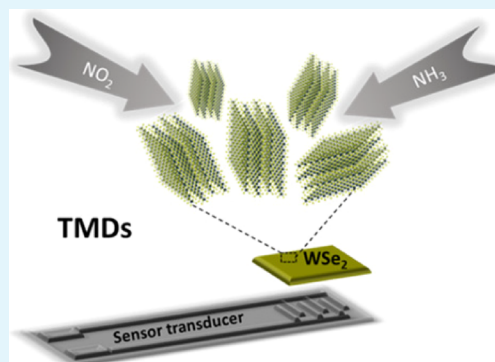

1. INTRODUCTION

Year by year, gas sensors have known tremendous developments in terms of sensing materials, size, power consumption, and fabrication costs. They are becoming indispensable items in the monitoring of indoor and outdoor toxic gases and thus play an increasing role in environmental monitoring, air quality control, or in safety and security applications.^{1–4} Among the main toxic and air pollutant gases, we find nitrogen dioxide (NO₂) and ammonia (NH₃), which are generated from motor vehicle exhaust, refineries, power plants, and so forth. While nitrogen dioxide has a direct contribution in the formation of ground-level ozone in the troposphere, acid rain and is a precursor of inorganic ambient particulate matter, ammonia contributes to acidification, eutrophication and is also a precursor for the formation of ammonium salts, a harmful form of fine particulate matter.^{5–7} For instance, exposure to nitrogen dioxide and ammonia may cause chronic bronchitis, respiratory irritation, mucous membrane inflammation syndrome, and asthma.^{8,9} The odor thresholds of NO₂ and NH₃ in

the air are around 400 and 40 ppb, respectively, while the threshold limit values (TLV) have been set by the Occupational Safety and Health Administration (OSHA) to 5 and 25 ppm, respectively.¹⁰ Exposure to high concentrations of these gases is a serious health threat. Hence, developing a new generation of gas sensors that can monitor such pollutant gases in real time and can detect concentrations from as low as a few parts per billion to several hundred parts per million in the air is of strong industry demand. In this context, chemiresistive sensors based on nanostructured metal oxide semiconductors, such as WO₃, ZnO, SnO₂, and In₂O₃, only to cite a few^{5,11–13} have been extensively used for detecting pollutant gases, owing

Received: September 9, 2022

Accepted: November 22, 2022

Published: December 5, 2022



to their advantages of sensitivity, low cost, simple fabrication process, and reliability. They were launched as building block materials for gas sensors, owing to their high surface-to-volume ratio, low number of defects, electron confinement effect, and so forth.^{14–16} However, their lack of selectivity and humidity cross-sensitivity remain the major drawbacks to overcome. Additionally, these nanomaterials are normally operated at 100–400 °C, leading to high power consumption and reduced sensor stability and lifetime, owing to thermally induced changes in morphology and poisoning effects. These drawbacks limit the adoption of metal oxide nanomaterial chemiresistors in wider real-time applications.

In a quest for overcoming such drawbacks, researchers have recently drawn toward atomically layered two-dimensional (2D) transition metal dichalcogenide (TMD) nanomaterials. TMDs possess unique properties such as semiconducting properties, direct band gaps, and high specific surface areas because of their sheet-like structures with large basal planes and highly reactive edges.^{17,18} TMDs consist of a metal atomic layer (such as Mo, W, Hf, Ti, Zr, V, Nb, Ta, Re, etc.) collocated between two chalcogen atomic layers (S, Se, or Te), and then, these 2D trilayers may appear stacked in multilayer structures because of van der Waals interactions.¹⁹ Among the TMD nanomaterials that have proven their feasibility as a gas-sensing element, we cite tungsten diselenide (WSe₂), which has ultimately sparked the interest of many researchers, especially in the detection of NO₂ and ammonia. Guo and co-workers²⁰ or Zhang and co-workers²¹ have reported ultrasensitive room temperature NO₂ sensors based on liquid-phase exfoliated WSe₂ nanosheets. Medina and co-workers²² synthesized wafer-scale WSe₂ monolayers toward phase-engineered hybrid WO_x/WSe₂ films with sub-ppb NO_x gas sensing by a low-temperature plasma-assisted selenization process. Ko and co-workers²³ developed high-performance NO₂ and NH₃ gas sensors based on three-layer WS₂ nanomaterials. Up to now, most of the reported studies have synthesized WSe₂ in a two-dimensional direction, in the form of mono or multilayer nanosheets. However, it has been reported that a vertical orientation (3D) of these nanomaterials is highly advantageous for gas sensing applications.^{24–26} Such an arrangement offers a large surface area to volume ratio with an enriched number of exposed edge sites and an increased number of defects that make the nanomaterial highly reactive with gas molecules.²⁷ In addition, the 3D arrangement of TMD nanosheets offers plenty of voids for gas diffusion. Indeed, gas adsorption at the edge sites of TMDs is more important compared to their basal plane, which has minimal dangling bonds, and, with the effect of thermodynamic forces, it is very challenging to expose the edges of 2D TMDs to the environment when these lie flat on the application substrate.^{7,17,28,29}

In this respect, there are two techniques that are mostly used for the growth of 3D assemblies of edge-enriched WSe₂ nanosheets: hydrothermal and atmospheric pressure chemical vapor deposition methods.^{30–32} Hydrothermal synthesis has the advantage of being low cost; however, it is a time-consuming technique (it involves multistep fabrication), and sometimes, it needs using hazardous precursors, which have hindered its development. In contrast, atmospheric pressure chemical vapor deposition (CVD) results in the synthesis of multi-layered TMDs with high yield, while enabling the control in the number of layers. Moreover, it is a catalyst-free technique, and it allows the direct growth of the material on

the application substrate, that is, the alumina sensor transducer.

Herein, we report, for the first time, on the successful synthesis of 3D assemblies of edge-enriched tungsten diselenide nanoflowers, using a combination of aerosol-assisted CVD and atmospheric pressure CVD techniques, for the development of bifunctional NO₂ and NH₃ gas sensors. The films were directly synthesized on alumina substrates, at atmospheric pressure without the need of any catalyst seeding. The grown films were studied in detail by using scanning electron microscopy (SEM), field emission SEM (FESEM), and high-resolution transmission electron microscopy (HRTEM) to analyze their morphology; X-ray diffraction (XRD) to determine their structure; and Raman and X-ray photoelectron spectroscopy (XPS) to define their composition. Additionally, the films were studied against small concentrations of NO₂ and NH₃ at low operating temperatures ranging from room temperature (i.e., 25 °C) to 150 °C. Besides, sensor performance was examined in the presence of ambient moisture. It is worth noting that only one previous paper²⁴ has reported so far the synthesis and use of 3D assemblies of WSe₂ nanoflowers for gas sensing. Finally, a comparison study between our work and the previous literature is reported and the gas sensing mechanism for both gases is introduced and discussed.

2. EXPERIMENTAL DETAILS

2.1. Material Synthesis. 3D assemblies of edge-enriched WS₂ nanoplatelets were synthesized in two steps. First, WO₃ nanowires were grown directly onto commercial alumina substrates (Ceram Tech GmbH, Germany) by using aerosol-assisted CVD method (AACVD). More details can be found in our previous reports.^{17,33} The front side of these substrates comprises screen-printed interdigitated platinum electrodes (electrode gap of 300 μm), while the backside comprises a screen-printed Pt heater (having a resistance of 8 Ω) to enable setting the operating temperature of the sensor. In the second step, the as-grown nanowires were subjected to a double selenization process via an ambient-pressure CVD technique to achieve a tungsten diselenide nanomaterial. The synthesis process is adopted from our previous research work.¹⁷ As in a typical selenization process, two boats containing the Se powder (purity 99%) were placed into two temperature zones, one boat at 40 °C and the other at 850 °C (in total 700 mg), along with the WO₃ nanofilm sample, which was placed at 850 °C prior to the selenization process, the quartz tube was flushed with a 0.475 L min⁻¹ argon flow for 1 h, in order to remove oxygen. Next, 0.150 L min⁻¹ of hydrogen (H₂) flow was added to the argon flow. In the first step of 30 min, the Se powder was placed at the 850 °C zone. The optimized second selenization step was performed by inserting the quartz tube in the hot zone of the furnace such that the Se powder placed at 40 °C reaches a 400 °C temperature zone. The sample remained at 850 °C as the quartz reactor was moved over a few centimeters. After the reaction, the H₂ flow was stopped, and the quartz tube was removed from the reactor (quartz tube) and was cooled with the argon flow for 1 h.

2.2. Characterization Techniques. The morphology of the as-grown WO₃ nanowires was examined using a scanning electron microscope (JEOL 7500F microscope operating at 15 kV), whereas after the selenization of WO₃ nanowires, the as-grown WSe₂ nanoplatelets were analyzed using a field-emission scanning electron microscope Hitachi 2000 and FEI Helios Nanolab 650. TEM studies were carried out on a TECNAI T20 microscope working under 200 kV. To prepare a sample, the material was scratched from the surface of an alumina substrate, dispersed in ethanol using sonication, and a droplet was put on a holey-carbon copper grid. For chemical phase analysis, XRD measurements were made using a Bruker-AXS D8-Discover diffractometer. The chemical composition of the WO₃

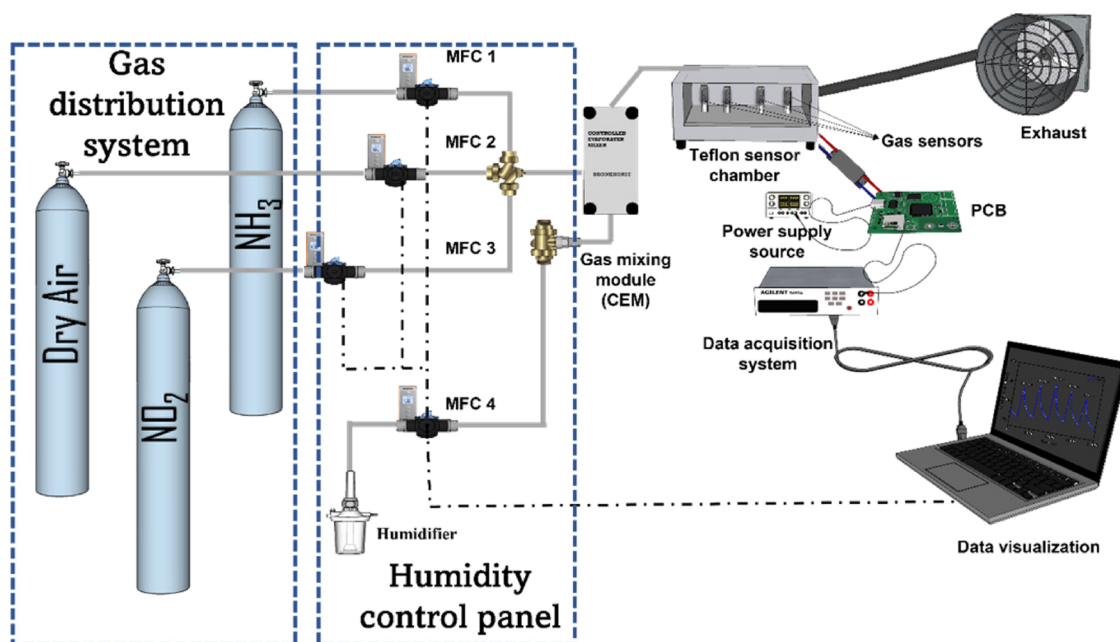


Figure 1. Schematic illustrating the home-made gas mixture, delivery, and sensor data acquisition systems.

nanowires and WSe₂ nanoplatelets was studied by XPS using an Escalab 250i Thermo Fisher spectrometer (Al K α 1486.68 eV). The O 1s, Se 3d, and W 4f core levels have been recorded at a pass energy of 20 eV, with 20 scans, on a spot size of 250 \times 250 μ m. A flood gun has been used for charge compensation and no additional energy shifting is applied to the spectra. The authors are aware of the recent warnings about XPS analysis on insulating samples.^{34–36} The spectra are analyzed with Thermo Avantage software, considering a Shirley background. The Raman spectra were obtained using a Renishaw in Via, laser 514 nm, ion argon-Novatech, 25 mW.

2.2.1. Gas Sensing Device Fabrication and Gas Sensing Measurements. The gas sensing characteristics of the fabricated WSe₂ nanoflower sensors were measured by using a homemade gas-sensing detection system. A schematic diagram of the home-made gas sensing detection system is shown in Figure 1. The as-fabricated sensor was placed inside a Teflon test chamber of 35 mL in volume. This testing chamber was connected to a fully automated, continuous gas flow measurement set-up able to supply diluted gas mixtures as well as humidified gas mixtures using a mass flow controller (Bronkhorst High-Tech B.V.) and electro valves. The gases employed for testing were used from calibrated gas cylinders balanced in dry synthetic air (Air Premier purity: 99.999%). The operating temperature of the sensor was controlled by connecting its heater to an external power supply (Agilent, model 3492A).

The sensing measurements were done by recording the change in electrical resistance of the sensor upon exposure to several different concentrations of target gases such as NO₂, NH₃, H₂, CO, and C₆H₆ at different operating temperatures (room temperature, 100 and 150 °C). A sensor was kept in a dry airflow for a period of 2 h before performing gas sensing measurements to stabilize its baseline resistance. Then, the sensor was exposed to a given concentration of a gaseous species for 10 min followed by 50 min exposure to dry air to regain and stabilize its baseline. The electrical resistance of the sensor was measured by using an Agilent-34972A multimeter. The gas flow and humidity were controlled using mass-flow controllers (MFC). Throughout the tests, the overall flow rate was maintained at 100 mL/min. To evaluate humidity interference, certain tests were done in a humid environment (e.g., 50% RH at 25 °C). While the sensor was exposed to varying concentrations of NO₂ and NH₃, the humidity level was kept constant. For an oxidizing gas, such as NO₂, the sensor relative response was calculated by using eq 1, while in the case of a reducing gas (such as NH₃), the gas sensing relative response value was calculated using eq 2. Even though the relative response, as

defined in eqs 1 and 2, has been used throughout this paper, from now on, the term response is used for short.

$$\text{Response} = \frac{R_{\text{air}} - R_{\text{gas}}}{R_{\text{air}}} \times 100\% \quad (1)$$

$$\text{Response} = \frac{R_{\text{gas}} - R_{\text{air}}}{R_{\text{air}}} \times 100\% \quad (2)$$

Here, R_{air} and R_{gas} are, respectively, the real-time resistances of the sensor exposed to air and to a target gas. For practical applications, the response and recovery times are very important parameters. In this work, the response time of the sensor (T_{res}) is defined as the time taken by the sensor to reach 90% of the total resistance change when exposed to a target gas, and the recovery time (T_{rec}) is defined as the time required to recover from 90 to 10% of the total resistance change when the analyte is removed from the air flow.

3. RESULTS AND DISCUSSION

3.1. Material Characterization. The morphological and chemical characteristics of the as-fabricated tungsten diselenide nanomaterial were assessed through various techniques, discussed in detail in this section.

3.1.1. SEM and FESEM Characterization. The AACVD method was employed to grow adherent uniform films of tungsten trioxide nanowires on alumina substrates. A scanning electron microscope was used to analyze the morphology and microstructure of these nanowires, as presented in Figure 2a. The result demonstrates that the sensor substrate is homogeneously covered with thin nanowires of WO₃. Even when showing different tilt angles, nanowires show a tendency to grow with vertical orientation to the substrate. The length of as-grown nanowires is in the range of 6–7 μ m because these films are obtained using the same procedure as reported in our previous studies.^{17,37} Afterward, the as-grown WO₃ films were selenized to produce WSe₂ nanofilms, which were subsequently examined using a high-resolution scanning electron microscope (Figure 2b–d). It is evident from the results obtained that after undergoing the selenization process, the morphology of these nanowires changes completely, resulting

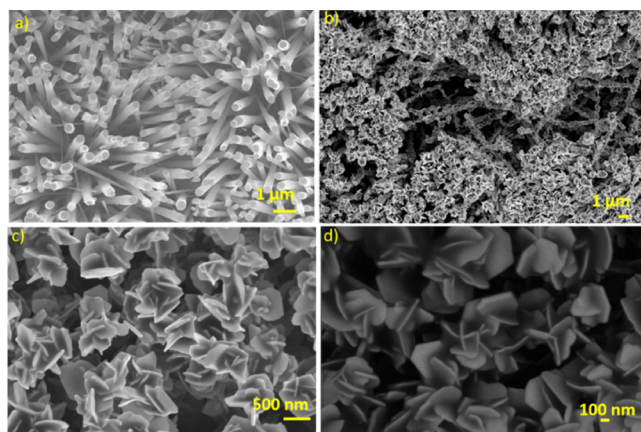


Figure 2. SEM and FESEM images depicting the growth of vertically aligned (a) WO_3 nanowires, (b) WSe_2 nanoplatelets, and (c,d) WSe_2 nanoflowers.

in platelets with well-defined shapes and sharp edges. Moreover, the layer-stacked bulk platelets grow vertically, similarly to WO_3 nanowires, as illustrated in Figure 2b. The results highlight that these platelets are evenly distributed and piled on top of one another, resulting in WSe_2 nanowires with platelet attachments covering the entire length of the nanowires, as seen in Figure 2b. Furthermore, SEM pictures reveal nanoplatelets assembled in the form of nanoflowers at the tips of these nanowires (Figure 2c). Also, the higher magnification image presented in Figure 2d reveals the thickness of these platelets, which is in the range of 40–50 nm.

3.1.2. TEM Characterization. The morphology, structure, and crystallinity of the as-prepared nanoflowered material were further investigated using TEM (Figure 3). It can be observed in Figure 3a that WO_3 nanowires completely transform into WSe_2 nanowires after undergoing the selenization process. These WSe_2 nanowires, which are about 10 μm in length, contain WSe_2 nanoplatelets along their entire length. These nanoplatelets arrange themselves in nanoflowers at the tips of the nanoneedles, as shown in SEM, but not in Figure 3a, certainly due to the TEM preparation. However, these nanoplatelets composing the petals of these nanoflowers are found dispersed on the grid, as shown in Figure 3b. In the inset of Figure 3b, the selected area electron diffraction (SAED) pattern of a single petal was acquired along the [100] axis and reveals only a single set of diffraction points arranged in a hexagonal symmetry, demonstrating its high crystallinity. The (001) planes in Figure 3c have a lattice spacing of about 0.29 nm, which is consistent with the 2H-phase of WSe_2 . Furthermore, Figure 3d displays an interlayer spacing of roughly 0.66 nm, corresponding to the (002) plane of the hexagonal WSe_2 .

3.1.3. Raman Characterization. Raman spectroscopy is a powerful and nondestructive tool for assessing nanomaterial quality and device feasibility. It is also very useful to determine the number of layers that contribute to the film thickness of a sample. In this respect, Raman spectroscopy was used to further examine the grown samples. To check for the presence of tungsten oxide in the selenized samples, the Raman spectra of the starting material (WO_3 nanowires) were compared to the films formed after the selenization process. Two spectra were obtained using a laser with an excitation wavelength of

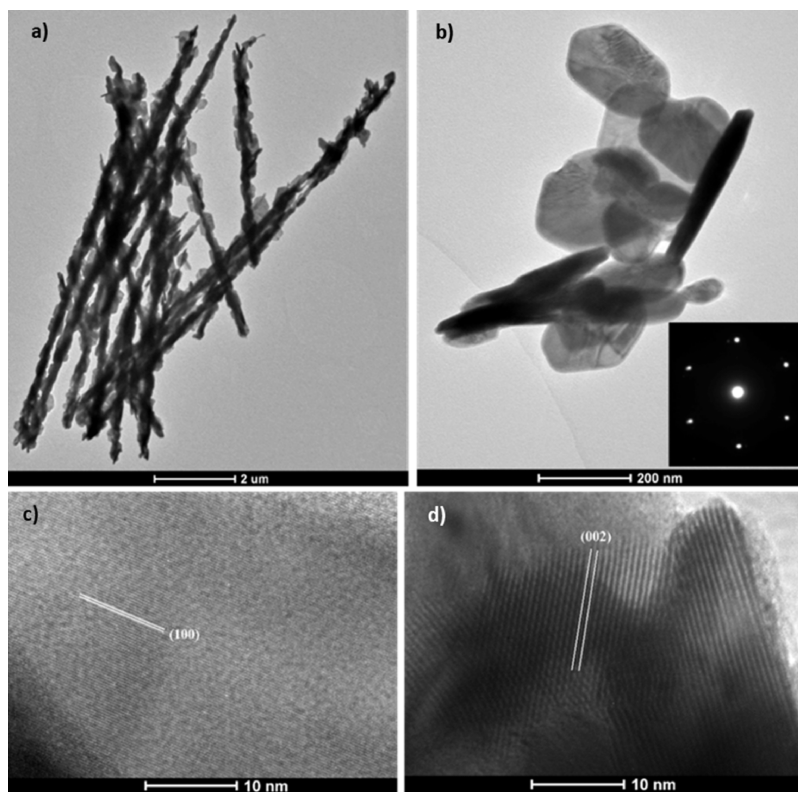


Figure 3. Low-magnification TEM images of (a) WSe_2 nanowires and (b) WSe_2 nanoflower petals with an inset of the SAED pattern along the [100] axis and high-resolution images of (c) a petal showing the (100) crystal planes and (d) layered structures of WSe_2 nanoplatelets composed of the petals with the (002) interlayer spacing.

532 nm, where the upper spectrum (Figure 4a) corresponds to the nanoflower film obtained after selenization of WO₃

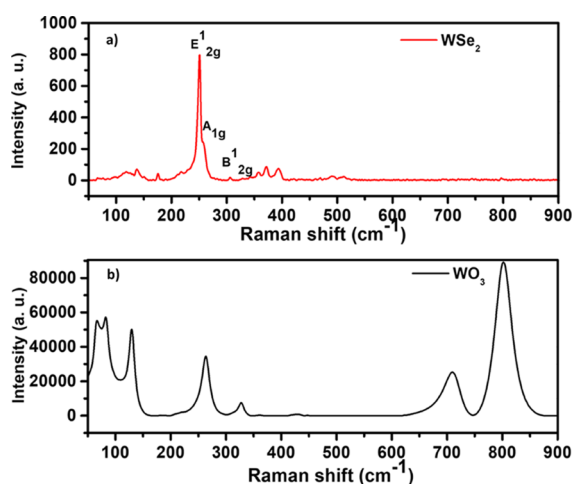


Figure 4. Raman spectra of (a) as-grown WSe₂ nanoflowered film and (b) WO₃ nanowires.

nanowires and the lower spectrum corresponds to the WO₃ nanowires (Figure 4b). As presented in Figure 4a, two main peaks were obtained, the peak at 251 cm⁻¹ corresponds to the E¹_{2g} (in-plane vibration of the Se and W atoms) while a small shoulder peak at 257.6 cm⁻¹ corresponds to the A_{1g} (out-of-plane vibration) modes. These are the two characteristic peaks associated with the presence of 2H-phase WSe₂. An additional peak was observed at 306 cm⁻¹ (B¹_{2g} mode) which has been linked to interlayer interactions. The absence of this peak is associated with the growth of monolayers, which is not the case here.^{37,38} The Raman analysis results are consistent with prior publications, demonstrating that the as-grown WSe₂ nanoflowers films are multilayered structures.^{39,40} Moreover, there was no other peak that indicated the presence of WO₃ impurities or any other impurity. Furthermore, for comparison purposes, the Raman spectrum of WO₃ NWs is shown in Figure 4b. All of the peaks (271, 327, 715, and 805 cm⁻¹) are indicative of the monoclinic tungsten trioxide phase, which is consistent with our previous reported studies.^{33,41}

3.1.4. XRD Analysis. The crystallographic structure and the purity of the WSe₂ nanoflower films are evaluated by the XRD technique. The XRD pattern obtained (Figure 5) reveals the

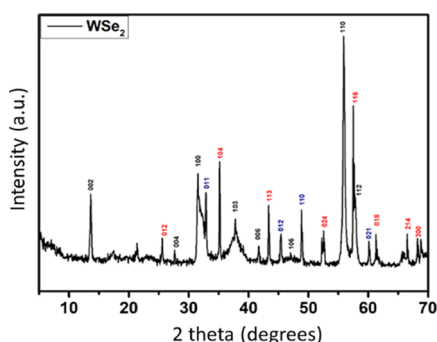


Figure 5. XRD diffractogram of as-grown WSe₂ nanoflowered film on alumina substrates with screen-printed platinum electrodes. Peaks whose crystal planes appear in red correspond to the alumina substrate on which the WSe₂ films were grown.

presence of intense peaks at 13.65°, 27.50°, 31.44°, 37.86°, 41.78°, 47.43°, 55.99°, and 57.92°, in agreement with the (002), (004), (100), (103), (006), (105), (110), (112) crystal planes of the hexagonal WSe₂. All the diffraction peaks are indexed to the ICDD card no 01-071-0600, confirming the presence of 2H phase WSe₂, marked with black color in the diffractogram. The high-intensity peaks imply a highly crystalline material, having a crystallite size above 400 nm, also reported earlier.⁴² Additionally, peaks corresponding to the alumina substrate were also detected and their lattice planes are highlighted in red. It was found that the peaks at 32.9°, 45.3°, 49.0°, and 60.3° can be indexed to the (011), (012), (110), (021) crystal planes, indicating the presence of small amounts of platinum selenide sulfide, Pt(SSe). These diffraction peaks are colored blue in the spectra and are referenced to the ICDD card no. 01-078-9794. The platinum is from the interdigitated electrodes screen-printed on the alumina substrate. Moreover, the absence of diffraction peaks attributable to a different phase than the 2H confirms that single crystalline 2H-WSe₂ is grown.

3.1.5. XPS Analysis. To further investigate the chemical composition of the as-prepared material, an XPS analysis was performed. The analysis of the sample before and after selenization is shown in Figure 6, confirming that the tungsten oxide nanomaterial has been completely transformed. Before selenization, the W4f signal (Figure 6a) is composed of a doublet centered at 35.5 and 37.7 eV, corresponding to W 4f_{7/2} and W 4f_{5/2} and an additional contribution at 41.2 eV, attributed to the W 5p_{3/2} level. These positions are in agreement with WO₃ formation.⁴³ On the O 1s level (Figure 5b), an intense contribution at 530.3 eV, corresponding to WO₃, confirms the oxide production. Two additional peaks are observed at 531.9 and 533.5 eV, attributed to organic oxygen (C–O, C=O), which are most likely from synthesis. As expected, no selenium is present before the selenization steps (Figure 6c). However, after selenization, the W 4f signal shifts to a lower binding energy and exhibits a unique doublet contribution centered at 32.2 and 34.3 eV, which is consistent with the WSe₂ 2H phase formation, where the literature reports binding energies in the range 32.0 to 32.4 eV^{44,45} and up to 32.7 eV⁴⁶ for large, oxygen-free tungsten diselenide flakes. Following the WSe₂ 2H phase formation, the Se 3d signal is composed of a unique doublet contribution centered at 54.4 and 55.26 eV because of the Se 3d_{5/2} and Se 3d_{3/2} levels, respectively. After selenization, there is no evidence of significant oxygen presence. As a result, the presence of the 2H phase is confirmed by XPS, XRD, and Raman analyses, as the 1T (or 1T') phase exhibits W 4f and Se 3d signals that are slightly shifted to lower binding energies (≈31.9 eV for the W 4f signal and 53.6–54.1 eV for Se 3d).^{42,44,45}

In summary, the results of SEM and TEM demonstrate the growth of vertically aligned WSe₂ nanoflowers. Furthermore, the results from the XRD analysis reveal that the as-grown WSe₂ nanoflowers exhibit excellent crystallinity. The lack of diffraction peaks that can be associated to other phases also suggests that WSe₂ nanoflowers are single crystalline. We may also conclude that the WSe₂ nanoflowers have a multilayered structure based on the Raman and XRD findings.

3.1.6. Gas Sensing Results. **3.1.6.1. NO₂ Detection.** The gas sensing properties of the as-fabricated WSe₂ nanoflower sensors were evaluated using a homemade gas monitoring system (described in detail in the previous section). Choosing the optimal working temperature for a gas sensor is crucial for

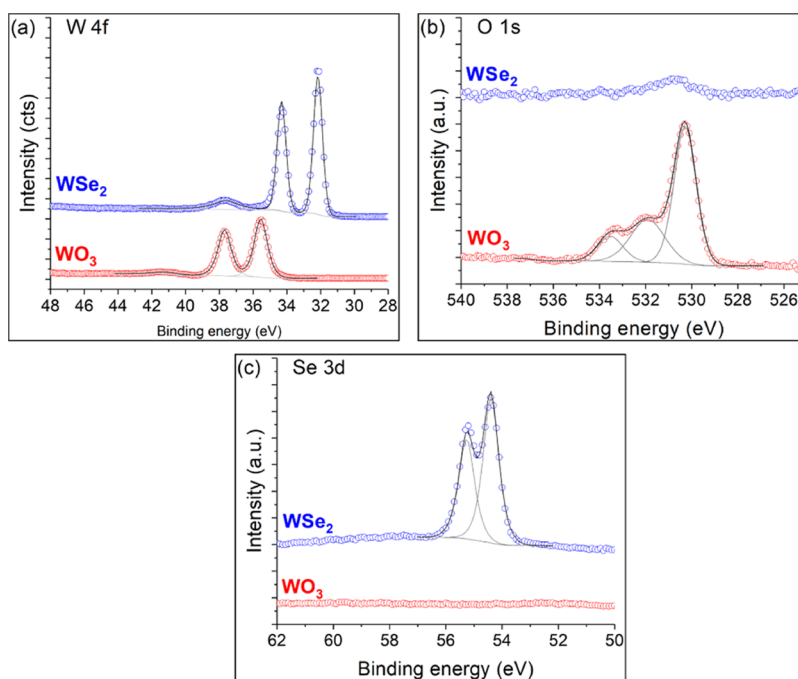


Figure 6. (a) W 4f, (b) O 1s, and (c) Se 3d XPS core-level spectra of WO_3 nanowires and WSe_2 nanoflowers.

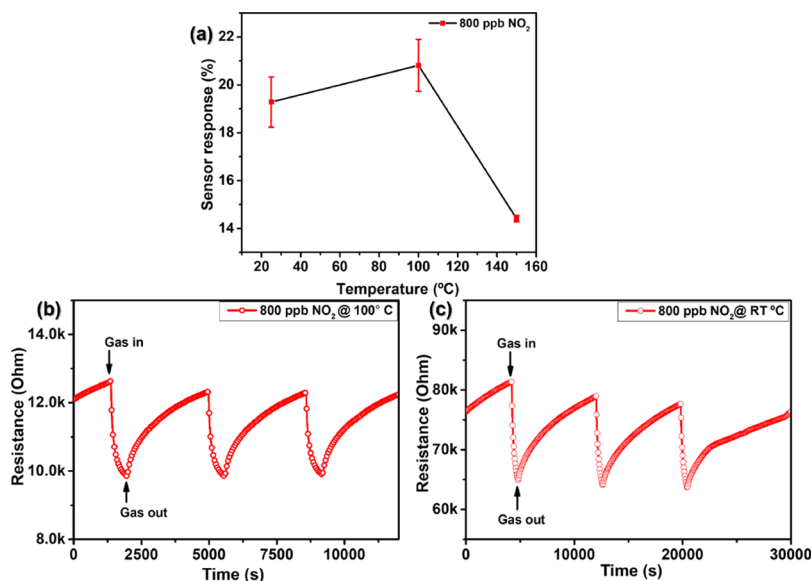


Figure 7. (a) Typical WSe_2 sensor response as a function of temperature toward NO_2 gas, (b) film resistance change as a function of time, toward 800 ppb of NO_2 at 100 °C, and (c) film resistance change as a function of time toward 800 ppb of NO_2 at 25 °C.

evaluating its performance because the sensitivity, selectivity, and response/recovery speed of gas-sensitive materials are all heavily dependent on the operating temperature. In order to identify a suitable operating temperature for detecting NO_2 , the temperature-dependent responses of the sensors to NO_2 were initially investigated. For doing so, we subjected our sensors to 800 ppb NO_2 in dry air balance and measured the resulting responses at various operating temperatures below 150 °C. Measuring a single gas concentration is a straightforward process for identifying an operating temperature that enhances response (and the signal-to-noise ratio). Setting 150 °C as the maximum operating temperature to be tested is due to the thermal instability of 2H- WSe_2 at higher temperatures as well as to prevent ambient oxidation of 2H-

WSe_2 . Investigating moderate operation temperatures is also beneficial for developing low-power devices.¹⁷

The sensor response to 800 ppb NO_2 gas is shown in Figure 7a at varying operating temperatures ranging from 25 to 150 °C. As demonstrated, the sensor response increases with an increase in operating temperature from 25 to 100 °C, and then, it decreases as the temperature is increased to 150 °C. The presence of potential selenium vacancies is attributed for the increased response at 100 °C. For instance, it has been reported in the literature that these vacancies promote NO_2 molecule adsorption at the WSe_2 surface, thereby increasing the interaction with the target gas molecules.⁴⁷

Furthermore, the sensor response is calculated to be 18.5% at room temperature (25 °C), rising to more than 20.5% at

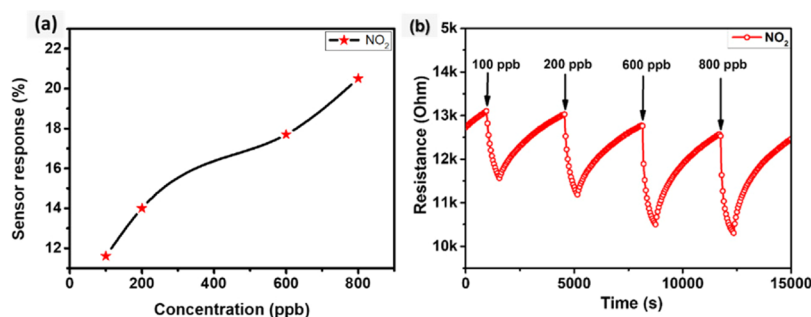


Figure 8. (a) WSe₂ sensor response as a function of different NO₂ concentrations and (b) film resistance change as a function of time, toward different NO₂ concentrations, at 100 °C.

Table 1. Comparison of the NO₂, NO, and NO_x Sensing Performance of WSe₂ Nanomaterials with Other Sensing Materials^a

2D material	studied conc.	working temp. (°C)	response (%)	LoD (ppm)	gas detected	humidity cross-sensitivity test	response time	ref
WSe ₂ NFs	0.8 ppm	100	20.5 ± 1.44	0.1 (exper.)	NO ₂	response increases slightly under wet conditions	196 s	this work
WSe ₂ vertical ns	1 ppm	RT	34.6	0.04 (theor.)	NO ₂	response decreases with increase in R.H.	66 s	24
WSe ₂	2 ppm	RT	18.8	not available	NO ₂	not studied	not available	56
WSe ₂ vertical structure	500 ppm	RT +1 V	4.5	not available	NO	not studied	not available	57
hybrid WO _x /WSe ₂	25 ppm	RT	13	0.3 (theor.)	NO _x	not studied	250 s	22
WSe ₂ nanoscrews	1 ppm	RT	350	0.072 (theor.)	NO _x	not studied	120 s	58
WS ₂ nanosheets	5 ppm	160	121	0.2 (exper.)	NO ₂	decrease in sensor response under wet conditions	not available	49
WS ₂ aerogel	3 ppm	250	0.36 (ΔR/R ₀)	0.008 (theor.)	NO ₂	decrease in sensor response under wet conditions	120 s	59
MoS ₂ /graphene	5 ppm	150	1.08/5 ppm	1.2 (exper.)	NO ₂	not studied	not available	60
MoS ₂ /rGO hybrid	3 ppm	160	1.29 R _s /R _g	0.1 (exper.)	NO ₂	high humidity influence on sensing response	8 s	61
WS ₂ graphene aerogel	2 ppm	180	3%	0.01 ppb (theor.)	NO ₂	sensor response increases under wet conditions	100 s	62

^aNFs: nanoflowers; 5 L: 5 layers; ns: nanosheets; conc.: concentration; exper.: experimentally verified; theor.: theoretically calculated; LoD: limit of detection.

operating temperature of 100 °C before dropping to only 14.2% at 150 °C. Consequently, 100 °C has been determined to be the optimal operating temperature for the fabricated WSe₂ nanoflowered sensors for NO₂ gas detection. It is worthy to mention that when compared to various metal oxides and other TMD materials, this operating temperature is relatively low.^{48,49} The response curve of gas sensors as a function of their operating temperature often is bell-shaped. The adsorption of gas molecules at the active sites of the gas-sensitive nanomaterial, eventual reaction with surface species, and associated charge transfer are thermally activated processes. However, too high an operating temperature promotes the desorption of gas molecules or limits the diffusion depth of gas molecules into a porous gas-sensitive film, thus reducing response intensity.⁵⁰

Figure 7b,c shows an example of dynamic film resistance change in response to 800 ppb NO₂ gas, at 100 and 25 °C, respectively. When exposed to an oxidizing gas, such as NO₂, the WSe₂ sensor responds as a p-type semiconductor with decreasing resistance. The electron–acceptor characteristics of oxidizing gases like NO₂ can elucidate this behavior. When a p-type material is exposed to an oxidizing atmosphere, electrons are removed from the conduction band, increasing the hole density and decreasing the material's electrical resistance and

vice versa when exposed to a reducing atmosphere.¹⁷ Besides, it is observed that the sensor does not completely return to its baseline resistance when the target gas is withdrawn and the sensor is exposed to dry air; however, the baseline resistance is recovered when the temperature is raised to 100 °C. This is due to the fact that higher temperature promotes faster desorption of gas molecules, resulting in a faster recovery cycle. In addition, the sensor response and recovery time for 800 ppb NO₂ varied considerably with temperature. For instance, at room temperature, the response and recovery times toward 800 ppb of NO₂ gas are computed to be 411 and 5446 s (Figure S1a), respectively, while at 100 °C, they fall to 196 and 2218 s (Figure S1b). This decrease in response, as well as recovery times, is attributed to the much faster desorption of NO₂ gas molecules at an elevated temperature.

Furthermore, at an operating temperature of 100 °C, the sensors were tested against a wide range of NO₂ gas concentrations ranging from 0.1 to 0.8 ppm. As expected, increasing NO₂ concentrations leads to higher resistance changes, resulting in an enlarged sensing response. Figure 8 depicts the observed data, which indicate a superlinear increase in sensing response with each increase in gas concentration (Figure 8a).

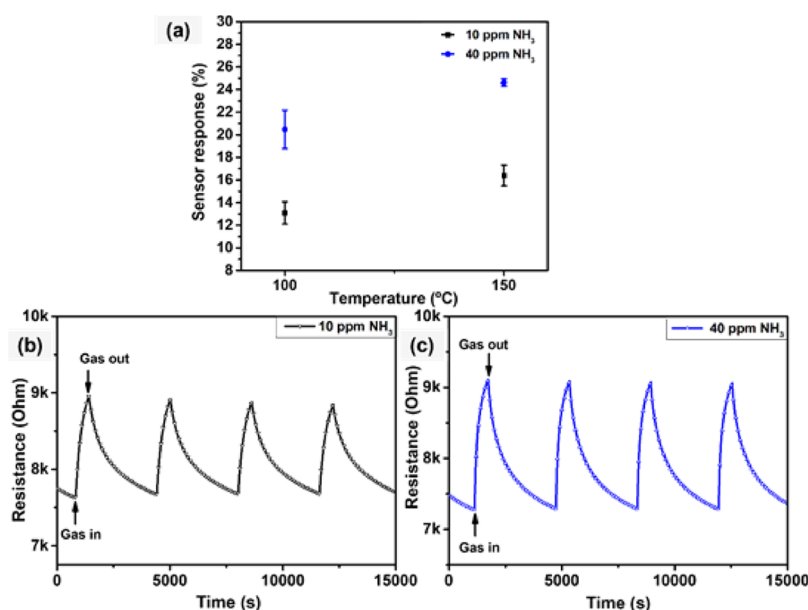


Figure 9. (a) WSe₂ sensor response as a function of temperature toward NH₃ gas, (b) film resistance change as a function of time toward (b) 10 ppm of NH₃ and (c) 40 ppm of NH₃, at 150 °C.

An example of the dynamic film resistance change over time in response to various NO₂ gas concentrations is presented in Figure 8b. The responses toward 0.1, 0.2, 0.6, and 0.8 ppm NO₂ were calculated to be 11.5, 14, 17.6, and 20.4%, respectively. It is worth mentioning that the sensor demonstrated remarkable sensitivity and high stability when detecting lower concentrations. The WSe₂ sensors, as shown in Figure 8b, can detect NO₂ gas concentrations as low as 0.1 ppm, which is substantially lower than the threshold exposure limit of NO₂ as recommended by the American Conference of Government Industrial Hygienists.⁴⁷ Henceforth, it can be deduced that the sensor exhibited an exceptionally low LoD which is below 100 ppb at a moderate operating temperature (100 °C).

Moreover, Table 1 gives more insights by comparing the performance in the detection of NO₂ reported in this paper with those found in the literature. The data reported in this table are comparable because unless clearly specified, sensors have been operated under similar conditions and the definitions of response, limit of detection, and response time are consistent throughout the references cited. From the results obtained, the fabricated WSe₂ sensors show outstanding gas responses with high sensitivity toward NO₂ detection and with LoD < 0.1 ppm when operated at 100 °C. Besides that, sensors remain functional and demonstrate acceptable sensitivity toward the targeted gas (NO₂) even when operated at room temperature.

3.1.6.2. NH₃ Sensing. Aside from NO₂ gas sensing, the performance of the WSe₂ nanoflower sensors against NH₃ gas was also investigated. Ammonia emissions are often related to livestock, food manufacturing, and textile industries. This species is of particular interest because of its adverse effects on human health and the environment at higher concentrations than NO₂. Nevertheless, the exposure to even low levels of ammonia can irritate the nose and throat.⁵¹ We investigated the optimal working temperature for the WSe₂ nanoflower sensors in the presence of NH₃ vapors. As shown in Figure 9a, the sensor response increases linearly with temperature, with practically little response at room temperature (Figure S2),

which can be expected due to rapid reaction rates at elevated temperatures. This behavior is more prominent when the concentration of the target gas is increased from 10 to 40 ppm. For instance, the gas response at 100 and 150 °C is 13 and 15.5%, respectively, toward 10 ppm NH₃ gas. Furthermore, as the NH₃ gas concentration is further increased to 40 ppm, the calculated response rises to values of 20.5 and 24.5% at 100 and 150 °C, respectively. This can be attributed to the hierarchical nanoflower structure, resulting in a high surface area which in turn enhances the active sites for NH₃ adsorption and surface reactions. Similar results were reported for self-assembled 2D and 1D WS₂ nanomaterials, which were synthesized by adopting a similar methodology, resulting in enhanced gas sensing properties toward NO₂ gas detection. Moreover, DFT calculations indicate that the adsorption energies of NO₂ and NH₃ onto a WSe₂ monolayer are −0.32 and −0.44 eV, respectively, thereby explaining that different optimal operating temperatures may apply for the two analytes tested.⁵² Therefore, considering the higher ammonia response recorded at 150 °C, this temperature has been considered for subsequent measurements with NH₃ gas. Higher operating temperatures were not considered for preventing the thermal degradation (oxidation) of the gas-sensitive films.

Figure 9b,c shows typical repeated response and recovery cycles for WSe₂ sensors toward 10 and 40 ppm of NH₃, respectively. As mentioned earlier, these sensors show p-type semiconducting properties resulting in increased electrical resistance upon exposure to NH₃ molecules (i.e., a reducing gas). Furthermore, sensors exhibit a repeatable response at each concentration, with the response and recovery time being substantially shorter for the higher NH₃ concentration (40 ppm) (Figure S3). For instance, for 10 ppm of NH₃, the WSe₂ sensor has a response time of 460 s and a recovery time of 2282 s (Figure S3a). For 40 ppm, the sensor has a response time of 396 s and a recovery time of 1917 s (Figure S3b). When response and recovery dynamics are limited by the diffusion of gas molecules within the gas-sensitive film, response and recovery times decrease with gas concentration.^{53,54} The lengthy recovery time is associated to the

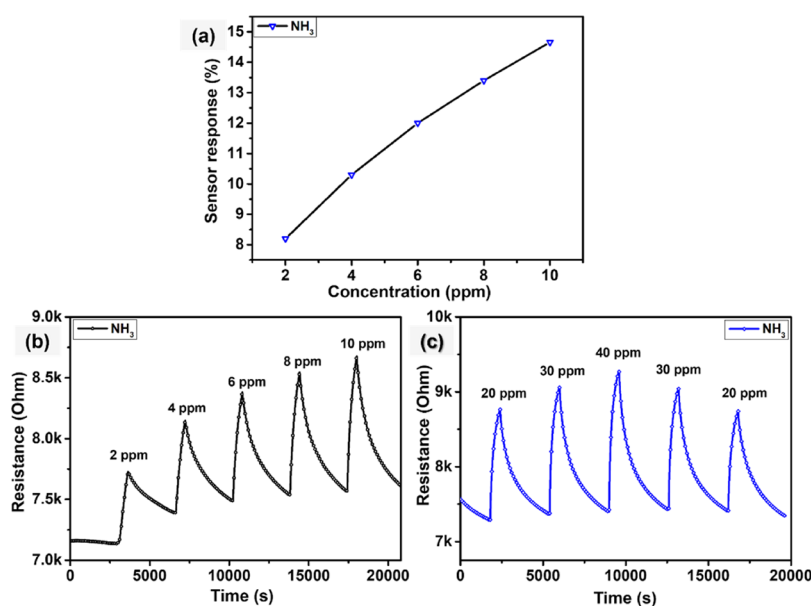


Figure 10. (a) WSe_2 sensor response as a function of NH_3 concentrations, (b,c) film resistance change as a function of time toward different concentrations of NH_3 at 150°C .

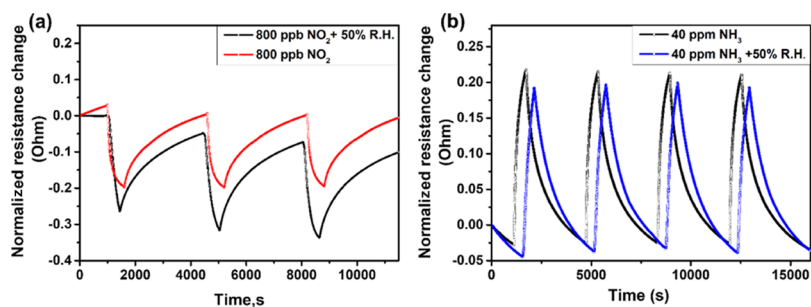


Figure 11. Dry and relative humidity cross-sensitivity to (a) 0.8 ppm NO_2 at 100°C and (b) 40 ppm NH_3 at 150°C .

strong interaction of NH_3 molecules and the surface of the sensitive material. While such an interaction promotes high sensitivity for analyte detection, this is at the cost of suffering from difficult desorption of adsorbed ammonia molecules.

Figure 10a demonstrates the response to varied NH_3 concentrations at a constant operating temperature of 150°C . The results reveal that as the concentration of analyte increases, so does the sensing response. During this measurement, a sensor was exposed to five successive NH_3 concentration pulses ranging from 2 to 10 ppm, as illustrated in Figure 10b. For 10 min, a diluted mixture of NH_3 in dry air was injected at concentrations of 2, 4, 6, 8, and 10 ppm. The WSe_2 sensor response was calculated to be 8.2, 10.3, 12, 13.4, and 14.5% toward 2, 4, 6, 8, and 10 ppm of NH_3 , respectively. In addition, as shown in Figure 9c, a sensor was evaluated for increasing and decreasing NH_3 gas pulses from 20 to 40 ppm and vice versa. During this measurement, the sensor was exposed to NH_3 pulses of 20, 30, 40, 30, and 20 ppm. As expected, the sensing response increases with increasing analyte concentration. For instance, the sensor response increased from 15.6 to 24.6% toward 10 and 40 ppm NH_3 , respectively. It is evident from the results obtained that the sensor shows reproducible and repeatable responses.

3.1.6.3. Humidity. To verify the practicability of the WSe_2 sensor, the influence of relative humidity on the sensor response toward NO_2 and NH_3 gases was also investigated.

The typical results are presented in Figure 11a,b, where sensors were tested at 100°C for 0.8 ppm NO_2 and 150°C for 40 ppm NH_3 in a 50% humidified air background. It was observed that the sensor response was increased from 20.5 to 26% and the baseline resistance was slightly decreased from 12 to 10 k Ω when the sensor was subjected to 0.8 ppm NO_2 gas in the presence of ambient moisture (50% R.H). Similar behaviors regarding the moisture-enhanced NO_2 response have previously been reported in the literature.⁵⁵ In Figure 11, sensor resistance changes are calculated, as defined in eqs 1 and 2, when under dry conditions. Under humid conditions, R_{air} is replaced by $R_{\text{air}50\%RH}$ and R_{gas} is replaced by $R_{\text{gas}50\%RH}$.

However, an extremely small change in sensor response as well as the baseline resistance is observed when exposed to NH_3 diluted in humidified air. The sensor response to 40 ppm NH_3 is calculated to be 24.1% in the presence of 50% RH, indicating an almost negligible change in its sensing response toward ammonia (response was 24.6% under dry conditions) and the baseline resistance was 7.4 k Ω in dry air and becomes 6.9 k Ω in the presence of 50% RH. This difference is in the range of the uncertainty associated to measurements. Moreover, water vapor is widely recognized for interfering with gas detection by changing the sensor electrical resistance in a similar way to a reducing gas. The great resilience of the sensor films, on the other hand, illustrates the WSe_2 nanoflower sensor strong reproducibility and stability for detecting NH_3 .

Table 2. Ammonia Gas Sensing Characteristics Reported in This Work Are Compared with Various TMDs Materials^a

2D material	studied conc. (ppm)	working temp. (°C)	response	LoD (ppm)	selectivity study	response time	humidity cross-sensitivity test	ref
WSe ₂ NFs	40	150	24.65% ± 0.31	2 ppm (exper.)	NO ₂ , C ₆ H ₆ , CO and H ₂	396 s	negligible effect of humidity	this work
3D WSe ₂ on 5 L Al ₂ O ₃	50	150	1.3 (R _g /R _a)	not available	NO ₂ , CO, C ₃ H ₆ O	not available	not studied	63
2D WSe ₂ on 5 L Al ₂ O ₃	50	150	1.1 (R _g /R _a)	not available	NO ₂ , CO, C ₃ H ₆ O	not available	not studied	63
MoS ₂ ns	10	100	30%	2 ppm (exper.)	CO and H ₂	193 s	not studied	28
WS ₂ aerogel	800	250	-0.8 (ΔR/R ₀)	13 ppm (theor.)	H ₂ and NO ₂	180 s	decrease in sensor response under wet conditions	59
Cu ₂ S thin films	500	25	19.78%	not available	not available	60 s	not studied	64
SnS ₂	100	200	7.4%	0.5 ppm (exper.)	CO ₂ , H ₂ , CH ₄ , ethanol, acetone	40.6 s	not studied	65
mixed-phase WS ₂	100	150	4.72	1 ppm (exper.)	C ₃ H ₈ O, C ₆ H ₅ Cl, C ₆ H ₁₂ O ₂ , C ₂ H ₅ OH, C ₇ H ₈	19 s	N/A ^b	66
WS ₂ thin films	5	25	-0.019% (ΔR/R ₀)	1.2 ppm (theor.)	not available	not available	not studied	67

^aNFs: nanoflowers; 5 L: 5 layers; ns: nanosheets; conc.: concentration exper.: experimentally verified; theor.: theoretically calculated. ^bThis study was conducted at a fixed low humidity level (28%) only and there are no data available to determine the effects of varying moisture levels on ammonia response.

vapors, even under humid conditions.⁵⁵ Also, it is worth mentioning that only very few studies,^{21,24,47} particularly for WSe₂-based gas sensors, have reported their behavior under humid conditions. None of the previously reported results for WSe₂ have reached such low humidity cross-sensitivity as we report here.

In this respect, when compared to prior research studies using WSe₂ and other TMDs material, the WSe₂ sensor fabricated in this work shows high performance (Table 2), with high sensitivity, low LoD, and outstanding (i.e., extremely low) humidity cross-sensitivity.

3.1.6.4. Selectivity. One of the most essential criteria in determining a sensor performance is selectivity. At 150 °C, we tested our sensors selectivity by exposing them to fixed concentrations of various species such as benzene vapors, carbon monoxide, and hydrogen. These gases or vapors are also of particular importance because they represent substantial health risks. For example, exposure to 5 ppm of benzene vapors for more than 15 min has been linked to the development of cancer.⁶⁸

The results in Figure 12 reveal the WSe₂ nanoflower sensor selectivity for NH₃ gas, with a maximum response of 24.65% and minimal responses to benzene and carbon monoxide. In addition to NH₃, the sensor exhibits some small reactivity to hydrogen gas (5%). However, it must be noticed that the hydrogen concentration tested was 20 times higher than the NH₃ concentration. The sensor also responds moderately (14%) to 0.8 ppm NO₂ gas at 150 °C, which could be ascribed to the dual selective nature of the WSe₂ sensor. Although the sensor shows dual selectivity toward NH₃ and NO₂ detection, it cannot be denied that the sensor is significantly more sensitive to NH₃ than to NO₂ at 150 °C. The ammonia and nitrogen dioxide concentration levels tested in this selectivity study have been selected close to the recommended exposure levels (REL) of the National Institute for Occupational Safety and Health (NIOSH). To address the current cross-sensitivity challenges and enhance the sensor selectivity toward NH₃ gas detection, functionalization with different nanomaterials might

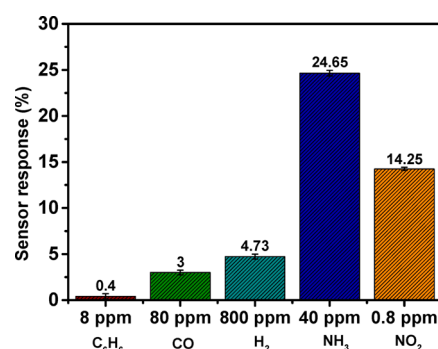


Figure 12. WSe₂ nanoflower sensor response based on exposure to 8 ppm C₆H₆, 80 ppm CO, 800 ppm H₂, 40 ppm NH₃, and 0.8 ppm NO₂ gas at an operating temperature of 150 °C.

be taken into consideration in this line of research. Furthermore, it is important to consider the sensor's great resistance toward humidity cross-sensitivity. In this respect, these research findings could pave a way for the development of WSe₂-based sensors that, in contrast to other TMDs-based gas sensors and many common metal oxide-based gas sensors, can operate at lower temperatures with ambient moisture.

Additionally, the stability of the sensors has been examined and the outcomes are depicted in Figure 13. The evolution of sensor response and baseline resistance was studied when NH₃ measurements (40 ppm) were repeated at regular intervals over a prolonged period (4 months). Even though some changes appear in the baseline resistance of WSe₂ sensors during the period in which long-term stability was studied, sensors display an almost constant response toward ammonia (computed according to eq 2) over 4 months. Throughout the whole long-term stability study, sensors were stored in the laboratory under ambient humidity and temperature conditions.

3.2. Gas Sensing Mechanism. A gas sensor performance is linked to its sensing mechanism. While in traditional metal oxide-based sensors, their gas sensing mechanism is based on a

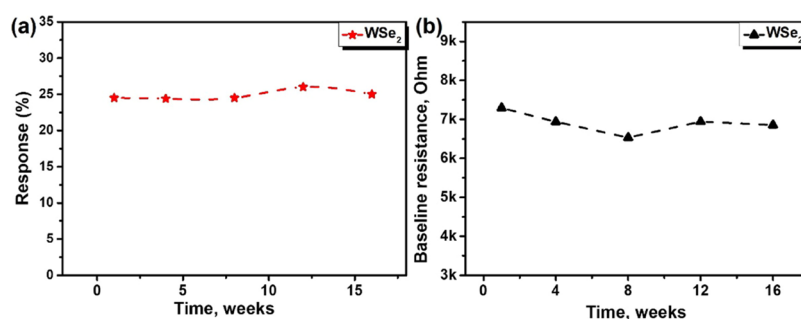


Figure 13. Long-term stability study. (a) Stability study for the WSe₂ sensor toward NH₃ gas over time, (b) evolution of the baseline resistance with time.

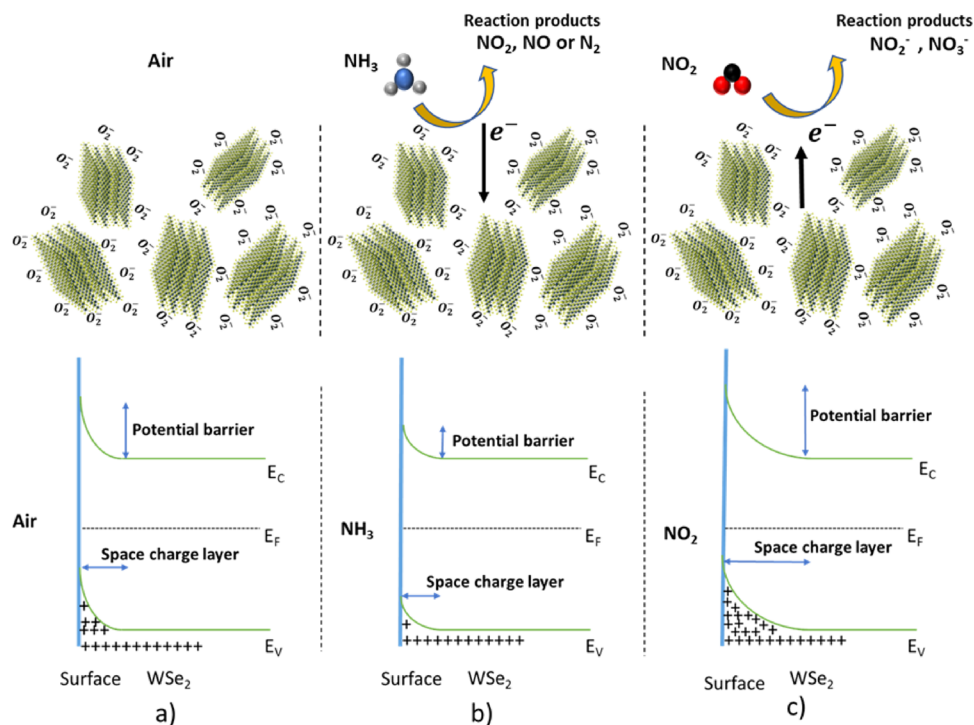


Figure 14. Schematic sketch of NH₃ and NO₂ gas sensing mechanisms and associated energy band diagrams for 2H WSe₂ (a) in air, (b) in the presence of NH₃, (c) in the presence of NO₂, where E_C , E_F , and E_V , correspond to the conduction band, Fermi level, and valence band.

surface reaction between the analyte gas molecules and pre-adsorbed oxygen ions on the metal-oxide surface. TMD-based gas sensors, on the other hand, depend completely on the adsorption/desorption and charge transfer processes between the target gas and the reactive sites in these materials.⁶⁷

The NH₃ gas sensing mechanism of 2D WSe₂ nanoflowers could be illustrated as the physisorption of the NH₃ gas molecules and charge transfer between WSe₂ nanoflowers and NH₃.³⁹ As a result of the induced charge transfer, the conductance of the material changes. To better understand the sensing mechanism, a concise schematic is illustrated in Figure 14.


Meanwhile, to fully comprehend the gas sensing mechanism, the presence of oxygen in ambient air cannot be neglected, as it is one of the prominent adsorbates during the gas sensing measurements.^{47,69} Therefore, the gas sensing mechanism of a 2H WSe₂ is based on two consecutive reactions occurring at the WSe₂ surface. Initially, when the sensor is exposed to dry synthetic air, oxygen molecules are adsorbed on the exposed surface.⁴⁷ From the literature, it is well known that the adsorbed oxygen species exists as O₂ (<150 °C), O (150–400

°C), and O²⁻ (>400 °C).¹² Because all the gas sensing measurements are performed at and below 150 °C (owing to the thermal degradation of WSe₂ material at a temperature above 200 °C), the adsorbed oxygen molecule is equivalent to O₂. The as-adsorbed oxygen molecule results in the extraction of electrons from the valence band of WSe₂ which results in the formation of a hole accumulation region (HAR) near the valence band, as shown in Figure 14a. The reaction can be represented by the following equation.




Afterward, when the sensor is exposed to NH₃ gas, the spontaneously adsorbed nucleophilic molecules donate electrons to the WSe₂ surface as well as they may react to the pre-adsorbed oxygen species present at the surface, resulting in the formation of free electrons. The free electrons that are released during the reaction combine with holes present in the valence band, thereby reducing the concentration of holes and subsequently increasing the resistivity of the sensor (as shown in Figure 8). As a result, the concentration of holes in the HAR region is reduced (Figure 14b). The p-type

semiconductor behavior of WSe₂ nanoflowers could be described by the following equation:⁷⁰



As the NH₃ gas concentration is further increased, the electron density increases as well, improving the sensor sensitivity to rising gas concentrations and decreasing the response and recovery time (see Figures 10b,c and S3). Furthermore, when the gas is removed and the sensor is exposed only to dry air at room temperature, there is an inadequate recovery of the WSe₂ sensor because of the difficulties in the desorption of surface species at room temperature. However, mild heating of the sensor at 150 °C resulted in complete baseline recovery. Therefore, 150 °C was chosen as the optimal working temperature toward NH₃ detection.

Contrary to this, when the sensor is exposed to NO₂ molecules, an opposite behavior is seen owing to the oxidizing nature of NO₂ gas. Because NO₂ molecules are electrophilic, they extract electrons from the valence band of 2D WSe₂ nanoflowers, causing electron deficit and a rise in hole concentration (Figure 14c). Consequently, the electrical conductance of the material increases, thereby resulting in a decrease in sensor resistance, as shown in Figure 6 (where the baseline resistance of the WSe₂ nanoflower decreases when exposed to NO₂ gas). Similar to NH₃, NO₂ gas molecules might as well interact with the preabsorbed oxygen species at the WSe₂ surface, resulting in the formation of NO₃. In addition to reaction 3, other reactions occurring at the surface of WSe₂ can be described by the following equations:⁴⁷



Furthermore, both edge atoms and in-plane defects of WSe₂ have previously been demonstrated to be active sites for molecule adsorption, resulting in providing additional surface areas for gas adsorption, thereby enhancing the overall gas sensing. Moreover, these reactions are particularly prevalent at the 2H defect sites, mainly at the Se vacancies. These vacancies contribute to the carrier charge transfer on the TMD surface and play a crucial role in the gas sensing mechanism because prior research has shown that the adsorption of NO₂ molecules is impossible without Se vacancies.⁷¹ This is further supported by DFT calculations, which demonstrated that in the absence of disulfide vacancies, the adsorption of N₂ molecules on MoS₂ is low.⁷² Despite the lack of research in the case of WSe₂, current studies on MoS₂ suggest that sulfur vacancies are one of the major defects in MoS₂ because of their low formation energy.

Gas sensing might also benefit from the active sites on the edges of these 2D materials. The 2D morphology of the WSe₂ nanoflowers that are attached to the 1D WSe₂ nanowires plays a significant role in providing a high surface area for the adsorption of these gaseous molecules (NO₂ and NH₃). Similar reports in the literature have revealed enhanced gas sensing characteristics of vertically distributed MoS₂ nanostructures supported by vertically arranged carbon nanotubes in comparison to horizontally arranged MoS₂.⁷³ Moreover, in our previous studies, we have reported enhanced gas sensing properties of 2D assemblies of WS₂ nanoflowers on 1D nanowires in comparison to the more closely packed nanoflake assembly.¹⁷

Pristine TMD nanomaterials such as MoTe₂, MoS₂, and WS₂ have been found to be sensitive to nitrogen dioxide and ammonia. In contrast, such materials show weak responses toward other species such as carbon monoxide, hydrogen, or aromatic volatile organic compounds (a-VOCs).^{29,52} Unlike NH₃ and NO₂, other species such as CO, H₂, and a-VOCs too weakly interact with the surface and the edges of TMDs. This low interaction energy results in a weak charge transfer between the molecule and the TMD film, which translates into a small chemoresistive signal. Some authors have reported the doping (e.g., with phosphorous or palladium) of TMDs as a way to enhance their response to CO⁷⁴ or H₂,⁷⁵ respectively. This could explain why our WSe₂ sensors operated at 150 °C are more sensitive to ammonia than to any of the other reducing gases tested.

4. CONCLUSIONS

We used an atmospheric pressure CVD approach to demonstrate a simple, effective, and high-yield synthesis process to obtain WSe₂ films. The morphology of as-grown WSe₂ is nanoflowers, which are composed of highly crystalline vertically aligned nanoplatelets. Furthermore, the synthesis approach is scalable and enables the direct growth of nanostructured material over functional substrates. The as-grown material is used to develop a chemoresistive type gas sensor having dual sensitivity toward NH₃ and NO₂ gas detection, depending on the operating temperature used. To the best of our knowledge, no previous research on WSe₂-based gas sensors has yielded such intriguing results. Moreover, the cross-sensitivity test revealed that H₂, C₆H₆, and CO have a negligible effect on NH₃ gas detection while the presence of NO₂ molecules shows some cross-sensitivity which could be assigned to the dual sensitive nature of the WSe₂ films. Moreover, water vapor at 50% relative humidity also resulted in having no interference to the measure of NH₃ gas, attesting to promising characteristics of WSe₂ for gas sensing applications. Henceforth, we believe that the results obtained in this study at moderate temperatures are intriguing and can provide a useful conceptual framework for detecting low concentrations of NH₃ in a real environment.

■ ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acsami.2c16299>.

Response and recovery times of WSe₂ toward 800 ppb NO₂; WSe₂ sensor response toward 10 ppm NH₃ gas at room temperature; and response and recovery time of the WSe₂ sensor toward (a) 10 ppm, (b) 40 ppm, NH₃ at 150 °C (PDF)

■ AUTHOR INFORMATION

Corresponding Authors

Fatima Ezahra Annanouch – Department d'Enginyeria Electronica, Universitat Rovira I Virgili, 43007 Tarragona, Spain; orcid.org/0000-0003-1533-6482; Email: fatimaezahra.annanouch@urv.cat

Jean-François Colomer – Laboratoire de Physique du Solide (LPS), Namur Institute of Structured Matter (NISM), University of Namur, 500 Namur, Belgium; Email: jean-francois.colomer@unamur.be

Eduard Llobet – Department d'Enginyeria Electronica, Universitat Rovira I Virgili, 43007 Tarragona, Spain; orcid.org/0000-0001-6164-4342; Email: eduard.llobet@urv.cat

Authors

Aanchal Alagh – Department d'Enginyeria Electronica, Universitat Rovira I Virgili, 43007 Tarragona, Spain

Ayrton Sierra-Castillo – Laboratoire de Physique du Solide (LPS), Namur Institute of Structured Matter (NISM), University of Namur, 500 Namur, Belgium

Emile Haye – Laboratoire d'Analyse par Réactions Nucléaires (LARN), Namur Institute of Structured Matter (NISM), Université de Namur, 5000 Namur, Belgium; orcid.org/0000-0001-9162-561X

Complete contact information is available at: <https://pubs.acs.org/10.1021/acsami.2c16299>

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

Funded in part by the Marie Skłodowska-Curie Actions (MSCA) Research and Innovation Staff Exchange (RISE) H2020-MSCA-RISE-2018-823895 “SENSOFT”, by MICINN and FEDER grant no. RTI2018- 101580-I00 and AGAUR grant no. 2017 SGR 418. A.A. is supported by a COFUND project the European Union's Horizon 2020 research and innovation program under the Marie Skłodowska Curie grant agreement No. 713679 and the Universitat Rovira i Virgili (URV). J.F.C. is a Senior Research Associate of the national funds for Scientific Research (FRS-FNRS, Belgium). E.L. is supported by the Catalan Institute for advanced studies (ICREA) via the 2018 Edition of the ICREA Academia Award. The technological SIAM (Synthesis, Irradiation, and Analysis of Materials) and Morph-IM platforms from the UNamur are acknowledged for XPS and electron microscopy analysis.

REFERENCES

- (1) Leiding, M.; Sauerwald, T.; Reimringer, W.; Ventura, G.; Schütze, A. Selective Detection of Hazardous VOCs for Indoor Air Quality Applications Using a Virtual Gas Sensor Array. *J. Sensors Sens. Syst.* **2014**, *3*, 253–263.
- (2) Chen, Y.-Z.; Wang, S.-W.; Yang, C.-C.; Chung, C.-H.; Wang, Y.-C.; Chen, S.-W. H.; Chen, C.-W.; Su, T.-Y.; Lin, H.-N.; Kuo, H.-C. An Indoor Light-Activated 3D Cone-Shaped MoS₂ Bilayer-Based NO Gas Sensor with Ppb-Level Detection at Room-Temperature. *Nanoscale* **2019**, *11*, 10410–10419.
- (3) Ghosh, R.; Gardner, J. W.; Guha, P. K. Air Pollution Monitoring Using near Room Temperature Resistive Gas Sensors: A Review. *IEEE Trans. Electron Devices* **2019**, *66*, 3254–3264.
- (4) Buckley, D. J.; Black, N. C. G.; Castanon, E. G.; Melios, C.; Hardman, M.; Kazakova, O. Frontiers of Graphene and 2D Material-Based Gas Sensors for Environmental Monitoring. *2D Mater.* **2020**, *7*, 32002.
- (5) Zhang, D.; Liu, Z.; Li, C.; Tang, T.; Liu, X.; Han, S.; Lei, B.; Zhou, C. Detection of NO₂ down to Ppb Levels Using Individual and Multiple In₂O₃ Nanowire Devices. *Nano Lett.* **2004**, *4*, 1919–1924.
- (6) Chatterjee, B.; Bandyopadhyay, A. Development of Zinc Oxide Sensors for Detecting Ammonia Gas in the Ambient Air: A Critical Short Review. *Environ. Qual. Manag.* **2016**, *26*, 89–105.
- (7) Alagh, A.; Annanouch, F. E.; Al Youssef, K.; Bittencourt, C.; Güell, F.; Martínez-Alanis, P. R.; Reguant, M.; Llobet, E. PdO and PtO Loaded WS₂ Boosts NO₂ Gas Sensing Characteristics at Room Temperature. *Sens. Actuators, B* **2022**, *364*, No. 131905.
- (8) Frampton, M. W.; Boscia, J.; Roberts, N. J., Jr.; Azadniv, M.; Torres, A.; Cox, C.; Morrow, P. E.; Nichols, J.; Chalupa, D.; Frasier, L. M.; Gibb, F. R.; Speers, D. M.; Tsai, Y.; Utell, M. J. Nitrogen Dioxide Exposure: Effects on Airway and Blood Cells. *Am. J. Physiol. Cell. Mol. Physiol.* **2002**, *282*, L155–L165.
- (9) Rahman, M. D. H.; Bråtveit, M.; Moen, B. E. Exposure to Ammonia and Acute Respiratory Effects in a Urea Fertilizer Factory. *Int. J. Occup. Environ. Health* **2007**, *13*, 153–159.
- (10) Occupational Safety and Health Administration, Permissible Exposure Limits – Annotated Tables <https://www.osha.gov/annotated-pels/table-z-1> (Accessed November 10, 2022).
- (11) Vallejos, S.; Selina, S.; Annanouch, F. E.; Gràcia, I.; Llobet, E.; Blackman, C. Aerosol Assisted Chemical Vapour Deposition of Gas Sensitive SnO₂ and Au-Functionalised SnO₂ Nanorods via a Non-Catalysed Vapour Solid (VS) Mechanism. *Sci. Rep.* **2016**, *6*, 28464.
- (12) Annanouch, F. E.; Haddi, Z.; Vallejos, S.; Umek, P.; Guttman, P.; Bittencourt, C.; Llobet, E. Aerosol-Assisted CVD-Grown WO₃ Nanoneedles Decorated with Copper Oxide Nanoparticles for the Selective and Humidity-Resilient Detection of H₂S. *ACS Appl. Mater. Interfaces* **2015**, *7*, 6842.
- (13) Ahmad, R.; Majhi, S. M.; Zhang, X.; Swager, T. M.; Salama, K. N. Recent Progress and Perspectives of Gas Sensors Based on Vertically Oriented ZnO Nanomaterials. *Adv. Colloid Interface Sci.* **2019**, *270*, 1–27.
- (14) Annanouch, F. E.; Haddi, Z.; Ling, M.; Di Maggio, F.; Vallejos, S.; Vilic, T.; Zhu, Y.; Shujah, T.; Umek, P.; Bittencourt, C.; Blackman, C.; Llobet, E. Aerosol-Assisted CVD-Grown PdO Nanoparticle-Decorated Tungsten Oxide Nanoneedles Extremely Sensitive and Selective to Hydrogen. *ACS Appl. Mater. Interfaces* **2016**, *8*, 10413.
- (15) Alenezi, M. R.; Henley, S. J.; Emerson, N. G.; Silva, S. R. P. From 1D and 2D ZnO Nanostructures to 3D Hierarchical Structures with Enhanced Gas Sensing Properties. *Nanoscale* **2014**, *6*, 235–247.
- (16) Gurlo, A. Nanosensors: Towards Morphological Control of Gas Sensing Activity. SnO₂, In₂O₃, ZnO and WO₃ Case Studies. *Nanoscale* **2011**, *3*, 154–165.
- (17) Alagh, A.; Annanouch, F. E.; Umek, P.; Bittencourt, C.; Sierra-Castillo, A.; Haye, E.; Colomer, J. F.; Llobet, E. CVD Growth of Self-Assembled 2D and 1D WS₂ Nanomaterials for the Ultrasensitive Detection of NO₂. *Sens. Actuators, B* **2021**, *326*, No. 128813.
- (18) Kim, Y.; Lee, S.; Song, J.; Ko, K. Y.; Woo, W. J.; Lee, S. W.; Park, M.; Lee, H.; Lee, Z.; Choi, H.; Kim, W. H.; Park, J.; Kim, H. 2D Transition Metal Dichalcogenide Heterostructures for P- and N-type Photovoltaic Self-powered Gas Sensor. *Adv. Funct. Mater.* **2020**, *30*, No. 2003360.
- (19) Choudhary, N.; Islam, M. A.; Kim, J. H.; Ko, T.-J.; Schropp, A.; Hurtado, L.; Weitzman, D.; Zhai, L.; Jung, Y. Two-Dimensional Transition Metal Dichalcogenide Hybrid Materials for Energy Applications. *Nano Today* **2018**, *19*, 16–40.
- (20) Guo, R.; Han, Y.; Su, C.; Chen, X.; Zeng, M.; Hu, N.; Su, Y.; Zhou, Z.; Wei, H.; Yang, Z. Ultrasensitive Room Temperature NO₂ Sensors Based on Liquid Phase Exfoliated WSe₂ Nanosheets. *Sens. Actuators, B* **2019**, *300*, No. 127013.
- (21) Yang, C.; Xie, J.; Lou, C.; Zheng, W.; Liu, X.; Zhang, J. Flexible NO₂ Sensors Based on WSe₂ Nanosheets with Bifunctional Selectivity and Superior Sensitivity under UV Activation. *Sens. Actuators, B* **2021**, *333*, No. 129571.
- (22) Medina, H.; Li, J.-G.; Su, T.-Y.; Lan, Y.-W.; Lee, S.-H.; Chen, C.-W.; Chen, Y.-Z.; Manikandan, A.; Tsai, S.-H.; Navabi, A.; Zhu, X.; Shih, Y.-C.; Lin, W.-S.; Yang, J.-H.; Thomas, S. R.; Wu, B.-W.; Shen, C.-H.; Shieh, J.-M.; Lin, H.-N.; Javey, A.; Wang, K. L.; Chueh, Y.-L. Wafer-Scale Growth of WSe₂ Monolayers Toward Phase-Engineered Hybrid WO_x/WSe₂ Films with Sub-Ppb NO_x Gas Sensing by a Low-Temperature Plasma-Assisted Selenization Process. *Chem. Mater.* **2017**, *29*, 1587–1598.
- (23) Ko, K. Y.; Park, K.; Lee, S.; Kim, Y.; Woo, W. J.; Kim, D.; Song, J.-G.; Park, J.; Kim, H. Recovery Improvement for Large-Area Tungsten Diselenide Gas Sensors. *ACS Appl. Mater. Interfaces* **2018**, *10*, 23910–23917.

- (24) Duan, Y.; Feng, S.; Zhang, K.; Qiu, J.; Zhang, S. Vertical Few-Layer WSe₂ Nanosheets for NO₂ Sensing. *ACS Appl. Nano Mater.* **2021**, *4*, 12043–12050.
- (25) Agrawal, A. V.; Kumar, N.; Venkatesan, S.; Zakhidov, A.; Manspeaker, C.; Zhu, Z.; Robles Hernandez, F. C.; Bao, J.; Kumar, M. Controlled Growth of MoS₂ Flakes from In-Plane to Edge-Enriched 3D Network and Their Surface-Energy Studies. *ACS Appl. Nano Mater.* **2018**, *1*, 2356–2367.
- (26) Lee, C. M.; Jin, C. H.; Ahn, C. H.; Cho, H. K.; Lim, J. H.; Hwang, S. M.; Joo, J. Enhanced Gas Sensing Performance of Surface-Activated MoS₂ Nanosheets Made by Hydrothermal Method with Excess Sulfur Precursor. *Phys. Status Solidi* **2019**, *216*, No. 1800999.
- (27) Xu, Y.; Xie, J.; Zhang, Y.; Tian, F.; Yang, C.; Zheng, W.; Liu, X.; Zhang, J.; Pinna, N. Edge-Enriched WS₂ Nanosheets on Carbon Nanofibers Boosts NO₂ Detection at Room Temperature. *J. Hazard. Mater.* **2021**, *411*, No. 125120.
- (28) Annanouch, F. E.; Alagh, A.; Umek, P.; Chafer, J. C. Controlled Growth of 3D Assemblies of Edge Enriched Multilayer MoS₂ Nanosheets for Dually Selective NH₃ and NO₂ Gas Sensors. *2022*, *2* (2), 11027–11039, DOI: 10.1039/d2tc00759b.
- (29) Deokar, G.; Vancsó, P.; Arenal, R.; Ravaux, F.; Casanova-Cháfer, J.; Llobet, E.; Makarova, A.; Vyalikh, D.; Struzzi, C.; Lambin, P.; Jouiad, M.; Colomer, J. F. MoS₂-Carbon Nanotube Hybrid Material Growth and Gas Sensing. *Adv. Mater. Interfaces* **2017**, *4*, No. 1700801.
- (30) Li, S.; Lee, J. K.; Zhou, S.; Pasta, M.; Warner, J. H. Synthesis of Surface Grown Pt Nanoparticles on Edge-Enriched MoS₂ Porous Thin Films for Enhancing Electrochemical Performance. *Chem. Mater.* **2019**, *31*, 387–397.
- (31) Agrawal, A. V.; Kumar, R.; Venkatesan, S.; Zakhidov, A.; Yang, G.; Bao, J.; Kumar, M.; Kumar, M. Photoactivated Mixed In-Plane and Edge-Enriched p-Type MoS₂ Flake-Based NO₂ Sensor Working at Room Temperature. *ACS Sens.* **2018**, *3*, 998–1004.
- (32) Wang, W.; Zhu, S.; Cao, Y.; Tao, Y.; Li, X.; Pan, D.; Phillips, D. L.; Zhang, D.; Chen, M.; Li, G.; Li, H. Edge-Enriched Ultrathin MoS₂ Embedded Yolk-Shell TiO₂ with Boosted Charge Transfer for Superior Photocatalytic H₂ Evolution. *Adv. Funct. Mater.* **2019**, *29*, No. 1901958.
- (33) Alagh, A.; Annanouch, F. E.; Colomer, J. F.; Llobet, E. 3D Assembly of WS₂ Nanomaterial for H₂S Gas Sensing Application. *IEEE Sens.* **2020**, *6*, 2–5.
- (34) Greczynski, G.; Hultman, L. X-Ray Photoelectron Spectroscopy: Towards Reliable Binding Energy Referencing. *Prog. Mater. Sci.* **2020**, *107*, No. 100591.
- (35) Greczynski, G.; Hultman, L. Compromising Science by Ignoring Instrument Calibration—Need to Revisit Half a Century of Published XPS Data. *Angew. Chem., Int. Ed.* **2020**, *59*, S002–S006.
- (36) Linford, M. R.; Smentkowski, V. S.; Grant, J. T.; Brundle, C. R.; Sherwood, P. M. A.; Biesinger, M. C.; Terry, J.; Artyushkova, K.; Herrera-Gómez, A.; Tougaard, S.; Skinner, W.; Pireaux, J. J.; McConville, C. F.; Easton, C. D.; Gengenbach, T. R.; Major, G. H.; Dietrich, P.; Thissen, A.; Engelhard, M.; Powell, C. J.; Gaskell, K. J.; Baer, D. R. Proliferation of Faulty Materials Data Analysis in the Literature. *Microsc. Microanal.* **2020**, *26*, 1–2.
- (37) Huang, J.-K.; Pu, J.; Hsu, C.-L.; Chiu, M.-H.; Juang, Z.-Y.; Chang, Y.-H.; Chang, W.-H.; Iwasa, Y.; Takenobu, T.; Li, L.-J. Large-Area Synthesis of Highly. *ACS Nano* **2014**, *8*, 923–930.
- (38) Liu, B.; Fathi, M.; Chen, L.; Abbas, A.; Ma, Y.; Zhou, C. Chemical Vapor Deposition Growth of Monolayer WSe₂ with Tunable Device Characteristics and Growth Mechanism Study. *ACS Nano* **2015**, *9*, 6119–6127.
- (39) Li, B.; Chen, X.; Su, C.; Han, Y.; Wang, H.; Zeng, M.; Wang, Y.; Liang, T.; Yang, Z.; Xu, L. Enhanced Dimethyl Methylphosphonate Detection Based on Two-Dimensional WSe₂ Nanosheets at Room Temperature. *Analyst* **2020**, *145*, 8059–8067.
- (40) Tonndorf, P.; Schmidt, R.; Böttger, P.; Zhang, X.; Börner, J.; Liebig, A.; Albrecht, M.; Kloc, C.; Gordan, O.; Zahn, D. R. T.; Michaelis de Vasconcellos, S.; Bratschitsch, R. Photoluminescence Emission and Raman Response of Monolayer MoS₂, MoSe₂, and WSe₂. *Opt. Express* **2013**, *21*, 4908.
- (41) Alagh, A.; Annanouch, F. E.; Llobet, E. Enhanced Gas Sensing Characteristics of Metal Doped WS₂ Nanoflowers. *IEEE Sens.* **2021**, 21–24.
- (42) Sierra-Castillo, A.; Haye, E.; Acosta, S.; Bittencourt, C.; Colomer, J. F. Synthesis and Characterization of Highly Crystalline Vertically Aligned WSe₂ Nanosheets. *Appl. Sci.* **2020**, *10*, 874.
- (43) Barreca, D.; Carta, G.; Gasparotto, A.; Rossetto, G.; Tondello, E.; Zanella, P. A Study of Nanophase Tungsten Oxides Thin Films by XPS. *Surf. Sci. Spectra* **2001**, *8*, 258–267.
- (44) Sokolikova, M. S.; Sherrell, P. C.; Palczynski, P.; Bemmer, V. L.; Mattevi, C. Direct Solution-Phase Synthesis of 1T' WSe₂ Nanosheets. *Nat. Commun.* **2019**, *10*, 712.
- (45) Wu, P. C.; Yang, C. L.; Du, Y.; Lai, C. H. Scalable Epitaxial Growth of WSe₂ Thin Films on SiO₂/Si via a Self-Assembled PtSe₂ Buffer Layer. *Sci. Rep.* **2019**, *9*, 8017.
- (46) Shallenberger, J. R. 2D Tungsten Diselenide Analyzed by XPS. *Surf. Sci. Spectra* **2018**, *25*, No. 014001.
- (47) Moumen, A.; Konar, R.; Zappa, D.; Teblum, E.; Perelshtein, I.; Lavi, R.; Ruthstein, S.; Nessim, G. D.; Comini, E. Robust Room-Temperature NO₂ Sensors from Exfoliated 2D Few-Layered CVD-Grown Bulk Tungsten Di-Selenide (2H-WSe₂). *ACS Appl. Mater. Interfaces* **2021**, *13*, 4316–4329.
- (48) Paolucci, V.; Emamjomeh, S. M.; Nardone, M.; Ottaviano, L.; Cantalini, C. Two-Step Exfoliation of WS₂ for NO₂, H₂ and Humidity Sensing Applications. *Nanomaterials* **2019**, *9*, 1363.
- (49) Liu, D.; Tang, Z.; Zhang, Z. Comparative Study on NO₂ and H₂S Sensing Mechanisms of Gas Sensors Based on WS₂ Nanosheets. *Sens. Actuators, B* **2020**, *303*, No. 127114.
- (50) Ahlers, S.; Müller, G.; Doll, T. Factors Influencing the Gas Sensitivity of Metal Oxide Materials. *Encycl. Sens.* **2006**, *3*, 413–447.
- (51) Timmer, B.; Olthuis, W.; Van Den Berg, A. Ammonia Sensors and Their Applications - A Review. *Sens. Actuators, B* **2005**, *107*, 666–677.
- (52) Mi, H.; Zhou, Q.; Zeng, W. A Density Functional Theory Study of the Adsorption of Cl₂, NH₃, and NO₂ on Ag₃-Doped WSe₂ Monolayers. *Appl. Surf. Sci.* **2021**, *563*, No. 150329.
- (53) Vilanova, X.; Llobet, E.; Alcubilla, R.; Sueiras, J. E.; Correig, X. Analysis of the Conductance Transient in Thick-Film Tin Oxide Gas Sensors. *Sens. Actuators, B* **1996**, *31*, 175–180.
- (54) Gardner, J. W. A Non-Linear Diffusion-Reaction Model of Electrical Conduction in Semiconductor Gas Sensors. *Sens. Actuators, B* **1990**, *1*, 166–170.
- (55) Li, X.; Li, X.; Li, Z.; Wang, J.; Zhang, J. WS₂ Nanoflakes Based Selective Ammonia Sensors at Room Temperature. *Sens. Actuators, B* **2017**, *240*, 273–277.
- (56) Wu, Y.; Joshi, N.; Zhao, S.; Long, H.; Zhou, L.; Ma, G.; Peng, B.; Oliveira, O. N.; Zettl, A.; Lin, L. NO₂ Gas Sensors Based on CVD Tungsten Diselenide Monolayer. *Appl. Surf. Sci.* **2020**, *529*, 2–8.
- (57) Chen, Y. Z.; Medina, H.; Wang, S. W.; Su, T. Y.; Li, J. G.; Yen, W. C.; Cheng, K. Y.; Kuo, H. C.; Shen, G.; Chueh, Y. L. Low-Temperature and Ultrafast Synthesis of Patternable Few-Layer Transition Metal Dichalcogenides with Controllable Stacking Alignment by a Microwave-Assisted Selenization Process. *Chem. Mater.* **2016**, *28*, 1147–1154.
- (58) Chen, Y. Z.; Lee, S. H.; Su, T. Y.; Wu, S. C.; Chen, P. J.; Chueh, Y. L. Phase-Modulated 3D-Hierarchical 1T/2H WSe₂ Nanoscrews by a Plasma-Assisted Selenization Process as High Performance NO Gas Sensors with a Ppb-Level Detection Limit. *J. Mater. Chem. A* **2019**, *7*, 22314–22322.
- (59) Yan, W.; Harley-Trochimczyk, A.; Long, H.; Chan, L.; Pham, T.; Hu, M.; Qin, Y.; Zettl, A.; Carraro, C.; Worsley, M. A.; Maboudian, R. Conductometric Gas Sensing Behavior of WS₂ Aerogel. *FlatChem* **2017**, *5*, 1–8.
- (60) Cho, B.; Yoon, J.; Lim, S. K.; Kim, A. R.; Kim, D. H.; Park, S. G.; Kwon, J. D.; Lee, Y. J.; Lee, K. H.; Lee, B. H.; Ko, H. C.; Hahm, M. G. Chemical Sensing of 2D Graphene/MoS₂ Heterostructure Device. *ACS Appl. Mater. Interfaces* **2015**, *7*, 16775–16780.

(61) Wang, Z.; Zhang, T.; Zhao, C.; Han, T.; Fei, T.; Liu, S.; Lu, G. Rational Synthesis of Molybdenum Disulfide Nanoparticles Decorated Reduced Graphene Oxide Hybrids and Their Application for High-Performance NO₂ Sensing. *Sens. Actuators, B* **2018**, *260*, 508–518.

(62) Yan, W.; Worsley, M. A.; Pham, T.; Zettl, A.; Carraro, C.; Maboudian, R. Effects of Ambient Humidity and Temperature on the NO₂ Sensing Characteristics of WS₂/Graphene Aerogel. *Appl. Surf. Sci.* **2018**, *450*, 372–379.

(63) Kang, M. J.; Kim, J. Y.; Seo, J.; Lee, S.; Park, C.; Song, S. M.; Kim, S. S.; Hahm, M. G. Atomic-Layered Tungsten Diselenide-Based Porous 3D Architecturing for Highly Sensitive Chemical Sensors. *Phys. Status Solidi RRL* **2019**, *13*, No. 1900340.

(64) Shinde, M. S.; Patil, D. R.; Patil, R. S. Ammonia Gas Sensing Property of Nanocrystalline Cu₂S Thin Films. *Indian J. Pure Appl. Phys.* **2013**, *51*, 713–716.

(65) Xiong, Y.; Xu, W.; Ding, D.; Lu, W.; Zhu, L.; Zhu, Z.; Wang, Y.; Xue, Q. Ultra-Sensitive NH₃ Sensor Based on Flower-Shaped SnS₂ Nanostructures with Sub-Ppm Detection Ability. *J. Hazard. Mater.* **2018**, *341*, 159–167.

(66) Meng, F.; Zhu, T.; Yuan, Z.; Qin, W.; Gao, H.; Zhang, H. Investigation of Mixed-Phase WS₂ Nanomaterials for Ammonia Gas Sensing. *IEEE Sens. J.* **2021**, *21*, 7268–7274.

(67) O'Brien, M.; Lee, K.; Morrish, R.; Berner, N. C.; McEvoy, N.; Wolden, C. A.; Duesberg, G. S. Plasma Assisted Synthesis of WS₂ for Gas Sensing Applications. *Chem. Phys. Lett.* **2014**, *615*, 6–10.

(68) Infante, P. F.; Benzene: An Historical Perspective on the American and European Occupational Setting. In *The Precautionary Principle in the 20th Century: Late Lessons from Early Warnings*; Earthscan Publication, 2013; pp 35–48.

(69) Burman, D.; Raha, H.; Manna, B.; Pramanik, P.; Guha, P. K. Substitutional Doping of MoS₂ for Superior Gas-Sensing Applications: A Proof of Concept. *ACS Sens.* **2021**, *6*, 3398–3408.

(70) Moumen, A.; Kumarage, G. C. W.; Comini, E. P-Type Metal Oxide Semiconductor Thin Films: Synthesis and Chemical Sensor Applications. *Sensors* **2022**, *22*, 1359.

(71) Zhao, P.; Kiriya, D.; Azcatl, A.; Zhang, C.; Tosun, M.; Liu, Y.; Hettick, M.; Kang, J. S.; McDonnell, S.; Kc, S.; Guo, J.; Cho, K.; Wallace, R. M.; Javey, A. Air Stable p-Doping of WSe₂ by Covalent Functionalization. *ACS Appl. Mater. Interfaces* **2014**, *8*, 10808–10814.

(72) Tongay, S.; Suh, J.; Ataca, C.; Fan, W.; Luce, A.; Kang, J. S.; Liu, J.; Ko, C.; Raghunathan, R.; Zhou, J.; Ogletree, F.; Li, J.; Grossman, J. C.; Wu, J. Defects Activated Photoluminescence in Two-Dimensional Semiconductors: Interplay between Bound, Charged, and Free Excitons. *Sci. Rep.* **2013**, *3*, 2657.

(73) Cho, S. Y.; Kim, S. J.; Lee, Y.; Kim, J. S.; Jung, W. B.; Yoo, H. W.; Kim, J.; Jung, H. T. Highly Enhanced Gas Adsorption Properties in Vertically Aligned MoS₂ Layers. *ACS Nano* **2015**, *9*, 9314–9321.

(74) Szary, M. J.; Florjan, D. M.; Bąbalek, J. A. Selective Detection of Carbon Monoxide on P-Block Doped Monolayers of MoTe₂. *ACS Sens.* **2022**, *7*, 272–285.

(75) Hao, L.; Liu, Y.; Du, Y.; Chen, Z.; Han, Z.; Xu, Z.; Zhu, J. Highly Enhanced H₂ Sensing Performance of Few-Layer MoS₂/SiO₂/Si Heterojunctions by Surface Decoration of Pd Nanoparticles. *Nanoscale Res. Lett.* **2017**, *12*, 567.

Recommended by ACS

Bidimensional Engineered Amorphous α -SnO₂ Interfaces: Synthesis and Gas Sensing Response to H₂S and Humidity

Valentina Paolucci, Carlo Cantalini, *et al.*

JUNE 25, 2022
ACS SENSORS

READ 

In Operando Investigation of the Concentration Dependent NO₂ Sensing Mechanism of Bi₂S₃ Nanorods at Low Temperatures and the Interference of O₃

Tamara Russ, Nicolae Barsan, *et al.*

OCTOBER 06, 2022
ACS SENSORS

READ 

ZnO Nanorods Grown on WS₂ Nanosheets for Chemiresistive H₂S Sensing

Neha Sakhuja, Navakanta Bhat, *et al.*

JUNE 30, 2022
ACS APPLIED NANO MATERIALS

READ 

Engineering CuMOF in TiO₂ Nanochannels as Flexible Gas Sensor for High-Performance NO Detection at Room Temperature

Haoxuan He, Yan-Yan Song, *et al.*

SEPTEMBER 13, 2022
ACS SENSORS

READ 

Get More Suggestions >